


**Definitions and notations relating to tactic polymers**

Journal:	<i>Pure and Applied Chemistry</i>
Manuscript ID	PAC-REC-19-04-09.R1
Manuscript Type:	Recommendation
Date Submitted by the Author:	26-Jun-2019
Complete List of Authors:	Fellows, Christopher; Univ. New England, Sch. Sci. & Technol, Armidale, NSW 2351, Australia Hellwich, Karl-Heinz; IUPAC, Division VIII Meille, Stefano; Politecnico di Milano Moad, Graeme; Commonwealth Scientific and Industrial Research Organisation, Manufacturing Nakano, Tamiki; Hokkaido University, Institute for Catalysis Vert, Michel; Universite de Montpellier
Keywords:	polymers, stereochemistry, tacticity, diad
Author-Supplied Keywords:	

SCHOLARONE™  
Manuscripts

1  
2  
3 Christopher M. Fellows, Karl-Heinz Hellwich,\* Stefano V. Meille, Graeme Moad,\* Tamaki  
4 Nakano, Michel Vert  
5

## 6 **Definitions and notations relating to tactic polymers (IUPAC Provisional** 7 **Recommendation)** 8 9

10  
11 **Abstract:** This document summarizes and extends definitions and notations for the  
12 description of tactic polymers and the diad structures of which they are composed. It formally  
13 recognizes and resolves apparent inconsistencies between terminology used in the polymer  
14 field to describe tactic polymers and terminology in more common use in organic chemistry.  
15 Specifically, the terms *m* and *r* diads are recommended to replace the terms *meso* and *racemo*  
16 diads. The definitions are also updated from those in the existing Stereochemistry Document  
17 to use the term ‘stereogenic centre’ rather than ‘chiral or prochiral atoms’. Further, the terms  
18 relating to tacticity have been defined for the constituent macromolecules rather than for the  
19 polymers composed of those macromolecules. This document hence also forms an addendum  
20 and corrigendum to the 1981 document ‘Stereochemical definitions and notations relating to  
21 polymers’.  
22  
23

24  
25 **Keywords:** polymer, stereochemistry, tacticity, diad  
26

### 27 **Article note:**

28 Sponsoring bodies: IUPAC Division of Chemical Nomenclature and Structure Representation  
29 and IUPAC Polymer Division, Sub-Committee on Polymer Terminology: see more details on  
30 p. ##.  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50

51 \*Corresponding authors: **Graeme Moad**, CSIRO Manufacturing, Clayton, Victoria 3168,  
52 Australia, email: [graeme.moad@csiro.au](mailto:graeme.moad@csiro.au). ORCID 0000-0002-4375-5580.

53 **Karl-Heinz Hellwich**, Beilstein-Institut zur Förderung der Chemischen Wissenschaften,  
54 Trakehner Str. 7 – 9, 60487 Frankfurt, Germany, email: [hellwich.iupac@gmx.de](mailto:hellwich.iupac@gmx.de). ORCID  
55 0000-0002-4811-7254.

56 **Christopher M. Fellows**, University of New England, Armidale, NSW 2351, Australia.  
57 ORCID 0000-0002-8976-8651.

58 **Stefano V. Meille**, Politecnico di Milano, Milano, Italy. ORCID 0000-0003-3071-6651.  
59  
60

1  
2  
3 **Tamaki Nakano**, Institute for Catalysis, Hokkaido University, Sapporo, 001-0021, Japan.  
4 ORCID 0000-0002-7843-4146.

5 **Michel Vert**, University of Montpellier - CNRS, 34093 Montpellier Cedex 5, France.  
6 ORCID 0000-0002-5751-2520.  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

For Peer Review Only

## SD-1 Introduction

In 1981 the former IUPAC Commission on Macromolecular Nomenclature published the document 'Stereochemical definitions and notations relating to polymers' [1], which was reprinted in the *Compendium of Macromolecular Nomenclature* better known as the first (1991) edition of the IUPAC 'Purple Book' [2] and again, with minor editorial corrections, in the second (2008) edition of the 'Purple Book' (the *Compendium of Polymer Terminology and Nomenclature*) [3].

With the current document it is intended to formally recognize and resolve apparent inconsistencies between terminology in the polymer field and that in more common use in organic chemistry, as described in the 'Basic terminology of stereochemistry' [4] and the IUPAC 'Blue Book' [5]. Recommendations are provided to minimize any potential confusion. Also, some of the definitions in [1-3] are inconsistent with those in the 'Glossary of Basic Terms in Polymer Science' published in 1996 [6] and hence with those in the *Compendium of Chemical Terminology* (the IUPAC 'Gold Book') [7]. Since both these documents [1,6] are reprinted in the 'Purple Book' [3], there is also inconsistency within that book.

The current document summarizes, revises and extends the basic definitions and notations relating to tactic polymers which were introduced in the Stereochemical Document [1-3]. It hence not only forms an addendum and corrigendum to the 1981 document [1-3], which it supersedes in part, but also replaces the corresponding definitions in [6,7].

Attention is also drawn to the fact that the sections relating to crystalline polymers in the Stereochemical Document [1-3] have been superseded with the publication of the revised 'Definitions of terms relating to crystalline polymers' [8] in 2011.

## SD-2 Terms for chirality centres

Centres or atoms referred to in the existing Stereochemical Document [1-3] as 'chiral centres' or 'chiral atoms' should be described as 'chirality centres' or as 'stereogenic centres' or 'stereogenic units' as appropriate depending on context [4]. Some relevant definitions from [4] are reproduced below.

### SD-2.1 chirality centre

An atom holding a set of ligands in a spatial arrangement which is not superposable on its mirror image. [4]

*Note:* Chirality centres are a subgroup of stereogenic centres, which are in turn a subgroup of stereogenic units.

### SD-2.2 stereogenic unit

A grouping within a molecular entity that may be considered a focus of stereoisomerism. [4]

*Note 1:* At least one of these must be present in every chiral chemical species (conversely, the presence of stereogenic units does not imply that the corresponding chemical species are chiral).

*Note 2:* Modified from [4].

### SD-2.3 diastereoisomerism

Stereoisomerism other than enantiomerism.

*Note 1:* Diastereoisomers (or diastereomers) are stereoisomers not related as mirror images.

*Note 2:* Diastereoisomers are characterized by differences in physical properties, and by some differences in chemical behaviour towards achiral as well as chiral reagents.

*Note 3:* Definition from [4].

### SD-2.4 diastereomorphism

The relationship between objects (or models) analogous to that between diastereoisomeric molecular entities.

*Note:* Definition from [4].

### SD-2.5 enantiomer

One of a pair of molecular entities which are mirror images of each other and non-superposable.

*Note:* Definition from [4].

### SD-2.6 enantiomorph

One of a pair of chiral objects or models that are non-superposable mirror images of each other.

*Note 1:* The adjective enantiomorph is also applied to mirror-image related groups within a molecular entity.


*Note 2:* Definition from [4].

## SD-3 Use of rotated Fischer projections in polymer publications

To eliminate possible confusion for those not familiar with the polymer literature, in particular, with the increased use of zigzag formulae with wedges to indicate configuration, it is recommended that rotated Fischer projections should not be used in any publication unless (a) it is specified as such at or before its first usage and (b) an appropriate reference (e.g., [1-3] alone or in combination with this document) is given to explain what is meant by a rotated Fischer projection.

### SD-3.1 Fischer projection


Projection formula in which vertically drawn bonds are considered to lie below the projection plane and horizontal bonds to lie above that plane. Thus for the molecule Cabcd:

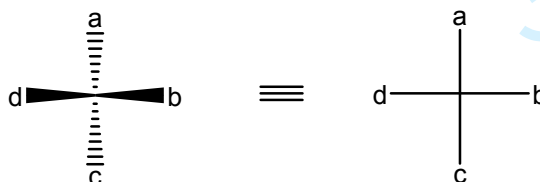

*Note:* Definition from [4].

### SD-3.2 rotated Fischer projection

Projection formula for macromolecules in which horizontal lines denote polymer backbone bonds. At each individual backbone carbon atom horizontal lines represent bonds directed below the projection plane, and vertical bonds direct above that plane.

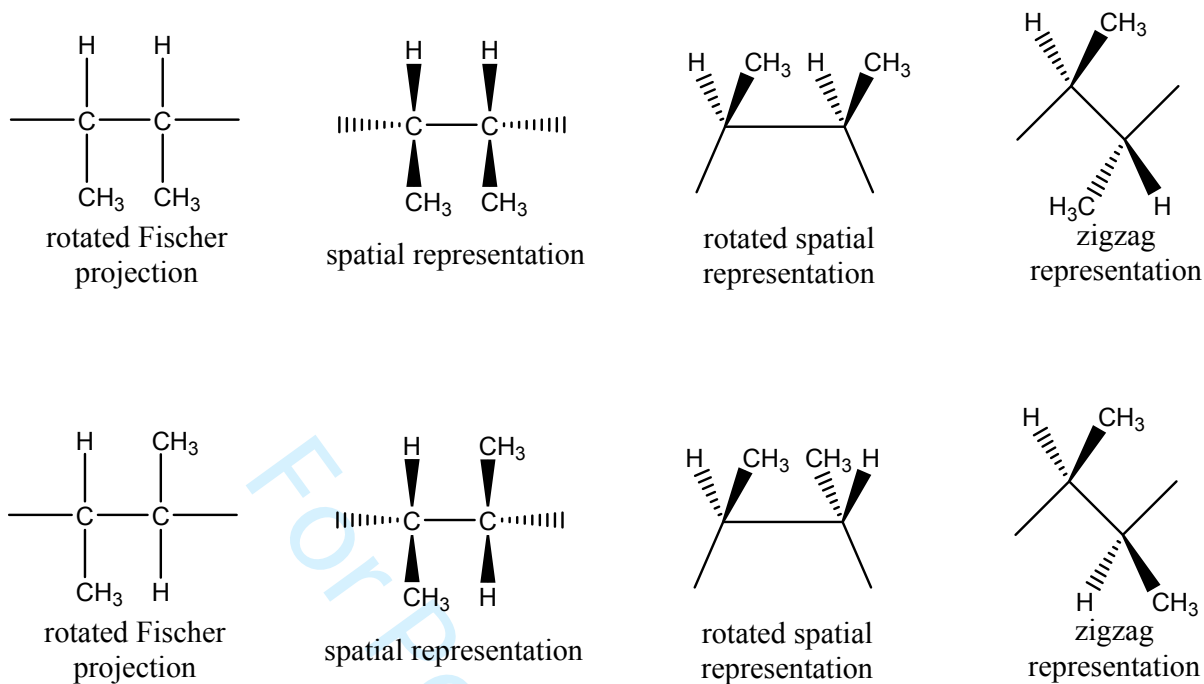

Note: Definition derived from the description in [1].

#### SD-4 Terms describing relative configuration (*m* and *r* structures)

Relative configuration is to be referred to, where appropriate, as *m* and *r* structures. The section in the Stereochemistry Document [1-3] entitled ‘*meso and racemo structures*’ should be retitled ‘*m and r structures*’.

The historical connection of the terms *m* and *r* to *meso* and *racemo*, respectively, when describing structures with a symmetrically-constituted connecting group between stereogenic centres of a polymer backbone, such as  $-\text{CH}_2-$ ,  $-\text{CH}_2-\text{CH}_2-$  and  $-\text{CR}_2-\text{CH}_2-\text{CR}_2-$ , is recognized. However, the usage of *meso* and *racemo* in this context is not acceptable because of the potential for confusion with the similar terms used in organic chemistry [4,5], in particular since a single molecule cannot be racemic. The terms *meso* and *racemo* are clearly incorrect if intended to describe structures where the connecting groups between stereogenic centres are not symmetrically-constituted in, for example, poly(methyloxirane), where the connecting group is  $-\text{CH}_2-\text{O}-$ .

It is now recommended that the relative configuration of consecutive, but not necessarily contiguous, constitutionally equivalent stereogenic centres be designated as *m* or *r*, as appropriate (Figure 1). The connecting group need not be symmetrically-constituted. Compound terms used for describing more complex structures, such as *mesodiisotactic* or *racemodiisotactic*, would then become, *m*-diisotactic or *r*-diisotactic, respectively.





**Figure 1.** Diagrammatic representation of individual *m* and *r* diads as rotated Fischer projections (left) and as zigzag Natta projections (right). The zigzag line  $-\text{Z}-$  represents a connecting group or bond, which need not be symmetrically-constituted.

#### SD-4.1 *m* diad

Pair of adjacent constitutionally equivalent stereogenic units that are of like configuration.

*Note:* Usage of the term *meso* diad for describing structures with a symmetrically-constituted connecting group is no longer acceptable because of the potential for confusion with the similar term used in organic chemistry to describe small molecules.

#### SD-4.2 *r* diad

Pair of adjacent constitutionally equivalent stereogenic units that are of unlike configuration.

*Note:* Usage of the term *racemo* diad for describing structures with a symmetrically-constituted connecting group is no longer acceptable because of the potential for confusion with the similar term used in organic chemistry to describe small molecules.

### SD-5 Terms describing tactic polymers

It is worth recalling a comment from the introduction to the Polymer Stereochemistry Document [1] which should be considered when dealing with the configuration and stereochemistry of polymers. It reads:

“In order to present clear concepts it is necessary that idealized definitions be adopted but it is recognized that the realities of polymer science must be faced. Deviations from ideality arise with polymers at both molecular and bulk levels in ways that have no parallel with the ordinary small molecules of organic or inorganic chemistry. Although such deviations are not explicitly taken into account in the definitions below, the nomenclature recommended can usefully be applied to the predominant structural features of real polymer molecules, if necessary with self-explanatory, if imprecise, qualifications such as ‘almost completely isotactic’ or ‘highly syndiotactic’. Although such expressions lack the rigour beloved of the purist, every experienced polymer scientist knows that communication in this discipline is impossible without them.”

Given its importance, the substance of this comment is now included as notes to the specific terms.

The definitions are also revised from those in the Stereochemistry Document [1-3] to use the term ‘stereogenic centre’ rather than ‘chiral or prochiral atoms’ (see SD-2). Further, the constituent macromolecules rather than the polymers composed of those macromolecules are defined.

The basic definitions of configurational unit, configurational base unit, configurational repeating unit, and stereorepeating unit are reiterated here [1-3]. They are, however, given in the wording of the ‘Gold Book’ [7] as updated in 1996 [6].

For ease of reference and to assist the reader, within section SD-5, cross-references to terms also defined in this section are denoted in italic typeface.

### SD-5.1 configurational unit

Constitutional unit having at least one site of defined configuration.

*Note 1:* The term configurational unit can also be used when the only stereogenic units are in side chains.

*Note 2:* Modified from [6,7]

### SD-5.2 configurational base unit

Constitutional repeating unit in a regular macromolecule, a regular oligomer molecule, a regular block, or a regular chain, the configuration of which is defined at least at one site of stereoisomerism in the main chain. [3,6]

*Note:* In a regular macromolecule, a configurational base unit corresponds to the constitutional repeating unit.

### SD-5.3 configurational repeating unit

Smallest set of successive *configurational base units* that prescribes configurational repetition at one or more sites of stereoisomerism in the main chain of a regular macromolecule, a regular oligomer molecule, a regular block, or a regular chain. [3,6]

*Note:* For a *syndiotactic macromolecule* the configurational repeating unit will be composed of two constitutional repeating units or configurational base units.

### SD-5.4 stereorepeating unit

*Configurational repeating unit* having defined configuration at all sites of stereoisomerism in the main chain of a regular macromolecule, a regular oligomer molecule, a regular block, or a regular chain. [3,6]

*Note 1:* Two *configurational units* that correspond to the same constitutional unit are considered to be enantiomorphic if they are non-superposable mirror images. Two non-superposable *configurational units* that correspond to the same constitutional unit are considered to be diastereomorphic if they are not mirror images.

*Note 2:* Modified from [1,2,3,6].

### SD-5.5 tactic macromolecule

Regular macromolecule in which essentially all *configurational repeating units* are identical.

*Note 1:* The prefix *ta-* is recommended to indicate a tactic macromolecule.

*Note 2:* Modified from [3,6].

### SD-5.6 tactic polymer

Polymer composed of *tactic macromolecules*. [6,7]

*Note 1:* The prefix *ta-* is recommended to indicate a tactic polymer.

*Note 2:* Modified from [1-3].

### SD-5.7 isotactic macromolecule

Regular macromolecule having only one species of *configurational base unit*, which has stereogenic units in the main chain in a unique arrangement with respect to its adjacent constitutional units.




*Note 1:* In an isotactic macromolecule, the *configurational repeating unit* is identical with the *configurational base unit*.

*Note 2:* A macromolecule consisting only of *m* diads is isotactic.

*Note 3:* It is common practice to use the term isotactic macromolecule to refer to macromolecules with predominantly *m* diads. When this is the case, it should be explicitly mentioned and, where possible, the tacticity should be quantitatively described. Use of the term isotactic to describe a macromolecule which has only a small excess of *m* diads is not acceptable.

*Note 4:* The prefix *it-* is recommended to indicate an isotactic macromolecule.

*Note 5:* Isotactic polypropylene can be depicted by a rotated Fischer Projection as follows.



*Note 6:* Adapted from [3,6].

### SD-5.8 isotactic polymer

Polymer composed of *isotactic macromolecules*. [6,7]

*Note 1:* The prefix *it-* is recommended to indicate an isotactic polymer.

*Note 2:* Modified from [1-3].

### SD-5.9 syndiotactic macromolecule

Regular macromolecule consisting of alternating enantiomorphic *configurational base units*, which have stereogenic centres in the main chain in a unique arrangement with respect to their adjacent constitutional units.


*Note 1:* In a syndiotactic macromolecule, the *configurational repeating unit* consists of two *configurational base units* that are enantiomorphic.

*Note 2:* A macromolecule consisting only of *r* diads is syndiotactic.

*Note 3:* It is common practice to use the term syndiotactic macromolecule to refer to macromolecules with predominantly *r* diads. When this is the case, it should be explicitly mentioned and, where possible, the tacticity should be quantitatively described. Use of the term syndiotactic to describe a macromolecule which has a small excess of *r* diads is not acceptable.

*Note 4:* The prefix *st-* is recommended to indicate a syndiotactic macromolecule.

*Note 5:* Syndiotactic polypropylene can be depicted by a rotated Fischer Projection as follows.

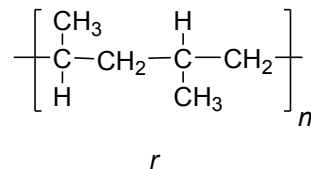

*Note 6:* Adapted from [3,6].

### SD-5.10 syndiotactic polymer

Polymer composed of *syndiotactic macromolecules*. [6,7]

*Note 1:* The prefix *st-* is recommended to indicate a syndiotactic polymer.

*Note 2:* Modified from [1-3].


### SD-5.11 heterotactic macromolecule

Regular macromolecule having a *configurational repeating unit* comprising four *configurational base units*, the first two stereogenic units of which are identical and enantiomorphic to the last two.

*Note 1:* A macromolecule consisting only of *m* and *r* diads in alternating sequence (i.e. *mr* and *rm* triads) is heterotactic.

*Note 2:* The prefix *ht-* is recommended to indicate a heterotactic macromolecule.

*Note 3:* A heterotactic polypropylene can be depicted by a rotated Fischer Projection as follows.

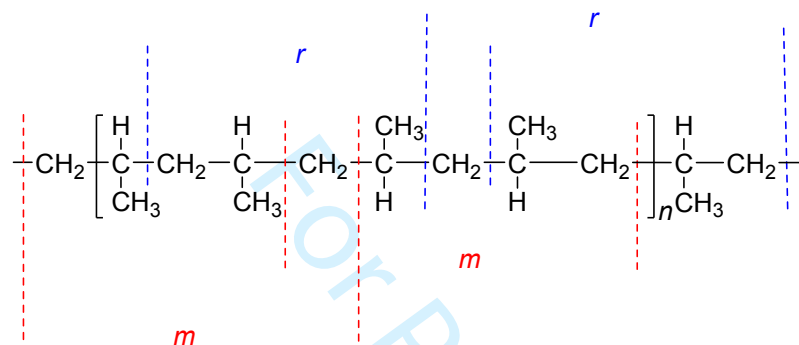

### SD-5.12 heterotactic polymer

Polymer composed of *heterotactic macromolecules*.

*Note:* The prefix *ht-* is recommended to indicate a heterotactic polymer.

### SD-5.13 atactic macromolecule

Regular macromolecule having essentially equal numbers of the possible enantiomorphic *configurational base units* which have stereogenic units in the main chain in a random sequence distribution.

*Note 1:* A macromolecule consisting of an essentially equal number of *m* and *r* diads in random sequence is atactic.

*Note 2:* It is common practice to use the term atactic macromolecule to refer to macromolecules where the number of possible configurational base units is almost equal, for example, macromolecules formed by radical polymerization of monosubstituted monomers. (They usually contain a small [2-5 %] but experimentally verifiable excess of *r* diads.) When this is the case, it should be explicitly mentioned and, where possible, the tacticity should be described quantitatively. Use of the term atactic to describe a macromolecule which departs significantly from a 1:1 ratio of *m* and *r* diads is not acceptable.

*Note 3:* The use of the term atactic to refer to a macromolecule where the stereochemical composition is simply unknown or not determined is not acceptable.

*Note 4:* The prefix *at-* is recommended to indicate an atactic macromolecule.

*Note 5:* Adapted from [1-3]. A different definition was given in [6].

### SD-5.14 atactic polymer

Polymer composed of *atactic macromolecules*. [6,7]

*Note 1:* The prefix *at-* is recommended to indicate an atactic polymer.

*Note 2:* Modified from [1-3].

## Memberships of sponsoring bodies

Membership of the IUPAC Division of Chemical Nomenclature and Structure Representation for the period 2018 – 2019 is as follows: **President:** A. T. Hutton (South Africa); **Past President:** K.-H. Hellwich (Germany); **Secretary:** R. S. Laitinen (Finland); **Titular Members:** M. A. Beckett (UK); E. C. Constable (Switzerland); T. Damhus (Denmark); R. T. Macaluso (USA); E. Nordlander (Sweden); A. P. Rauter (Portugal); M. M. Rogers (USA); **Associate Members:** E. Mansfield (USA); J. Nagy (Hungary); M. A. Strausbaugh (USA); K. T. Taylor (USA); C. A. Tovee (UK); J. Vohlídal (Czech Republic); **National Representatives:** F. Aricò (Italy); N. Burford (Canada); A. M. da Costa Ferreira (Brazil); S. Erdem (Turkey); S. Koo (Korea); R. Kruszyński (Poland); L. Meesuk (Thailand); M. A. Petrova (Bulgaria); E. Szabó (Slovakia); A. Yerin (Russia); **Ex Officio:** R. M. Hartshorn (New Zealand); G. P. Moss (UK).

Membership of the IUPAC Polymer Division Committee for the period 2018–2019 is as follows:

**President:** G. T. Russell (New Zealand); **Vice President:** C. K. Luscombe (USA); **Secretary:** M. G. Walter (USA); **Past President:** M. Buback (Germany); **Titular Members:** C. Fellows (Australia); R. C. Hiorns (France); R. Hutchinson (Canada); I. Lacík (Slovakia); N. Stingelin (USA); P. D. Topham (UK); Y. Yagci (Turkey); **Associate Members:** S. Beuermann (Germany); M. C. H. Chan (Malaysia); C. dos Santos (Brazil); D. S. Lee (South Korea); G. Moad (Australia); P. Théato (Germany); **National Representatives:** R. Adhikari (Nepal); J. He (China); M. Hess (Germany); V. Hoven (Thailand); C.-S. Hsu (Taipei, China); P. Mallon (South Africa); O. Philippova (Russia); M. Sawamoto (Japan); A. Sturcova (Czech Republic); J. van Hest (Netherlands).

Membership of the Subcommittee on Polymer Terminology during the preparation of these Recommendations (2009 – 2018) was as follows:

**Chair:** R. G. Jones (UK), 2006-2013; R. C. Hiorns (France), from 2014; **Secretary:** T. Kitayama (Japan), 2008-2009; R. C. Hiorns (France), 2010-2013; C. K. Luscombe (USA), 2014-2015; P. D. Topham (UK), from 2016; **Members:** V. Abetz (Germany); R. Adhikari (Nepal); G. Allegra (Italy); M. Barón (Argentina); R. Boucher (UK); P. Carbone (UK); M. C. H. Chan (Malaysia); T. Chang (Korea); J. Chen (USA); C. Fellows (Australia); A. Fradet (France); C. F. O. Graeff (Brazil); J. He (China); K.-H. Hellwich (Germany); M. Hess (Germany); P. Hodge (UK); W. Hu (China); A. D. Jenkins (UK); J.-I. Jin (Korea); J. Kahovec (Czech Republic); T. Kitayama (Japan); P. Kratochvíl (Czech Republic); P. Kubisa (Poland); M. Malinconico (Italy); J. B. Matson (USA); S. V. Meille (Italy); J. Merna (Czech Republic); G. Moad (Australia); W. Mormann (Germany); T. Nakano (Japan); C. K. Ober (USA); M. Peeters (Netherlands); S. Penczek (Poland); O. Philippova (Russia); M. D. Purbrick (UK); G. Raos (Italy); G. Russell (USA); C. dos Santos (Brazil); C. Scholz (USA); F. Schué† (France); S. Słomkowski (Poland); D. W. Smith (USA), R. F. T. Stepto‡ (UK); N. Stingelin (UK); A. Sturcova (Czech Republic); D. Tabak (Brazil); P. Théato (Germany); J.-P. Vairon (France); M. Vert (France); J. Vohlídal (Czech Republic); M. G. Walter (USA); E. S. Wilks (USA); W. J. Work (USA); M.-H. Yoon (Korea).

## Acknowledgements

The role of Aubrey D. Jenkins, Tatsuki Kitayama, and the late Robert F. T. Stepto at the inception of the project is gratefully acknowledged.

## References

- [1] A. D. Jenkins. 'Stereochemical definitions and notations relating to polymers (Recommendations 1980)', *Pure Appl. Chem.* **53**, 733 – 752 (1981); reprinted as chapter 2 in [2]; reprinted as chapter 2 in [3].
- [2] IUPAC. *Compendium of Macromolecular Nomenclature* (the 'Purple Book'). Ed. W. V. Metanomski, Blackwell Scientific Publications, Oxford, UK (1991).
- [3] IUPAC. *Compendium of Polymer Terminology and Nomenclature (IUPAC Recommendations 2008)* (the 'Purple Book'). Prepared for publication by R. G. Jones, J. Kahovec, R. Stepto, E. S. Wilks, M. Hess, T. Kitayama, W. V. Metanomski, with advice from A. Jenkins and P. Kratochvíl, RSC Publishing, Cambridge, UK (2008).
- [4] G. P. Moss. 'Basic terminology of stereochemistry (IUPAC Recommendations 1996)', *Pure Appl. Chem.* **68**, 2193 – 2222 (1996).
- [5] IUPAC. *Nomenclature of Organic Chemistry: IUPAC Recommendations and Preferred Names 2013* (the 'Blue Book'). Prepared for publication by H. A. Favre and W. H. Powell, Royal Society of Chemistry, Cambridge, UK (2014); errata: <https://www.qmul.ac.uk/sbcs/iupac/bibliog/BBerrors.html>.
- [6] A. D. Jenkins, P. Kratochvíl, R. F. T. Stepto, U. W. Suter. 'Glossary of basic terms in polymer science (IUPAC Recommendations 1996)', *Pure Appl. Chem.* **68**, 2287 – 2311 (1996); reprinted with some changes as chapter 1 in [3].
- [7] IUPAC. *Compendium of Chemical Terminology* (the 'Gold Book'), 2nd ed. Compiled by A. D. McNaught and A. Wilkinson. Blackwell Science, Oxford, UK (1997); XML on-line corrected version: <http://goldbook.iupac.org> (2006) created by M. Nic, J. Jirat, B. Kosata; updates compiled by A. D. Jenkins. (<https://doi.org/10.1351/goldbook>).
- [8] S. V. Meille, G. Allegra, P. H. Geil, J. He, M. Hess, J.-I. Jin, P. Kratochvíl, W. Mormann, R. Stepto. 'Definitions of terms relating to crystalline polymers (IUPAC Recommendations 2011)', *Pure Appl. Chem.* **83**, 1831 – 1871 (2011).